

Co-existing chiral and collinear phases in a distorted triangular antiferromagnet

A. I. Smirnov,¹ L. E. Svistov,¹ L. A. Prozorova,¹ A. Zheludev,² M. D. Lumsden,² E. Ressouche,³ O. A. Petrenko,⁴ K. Nishikawa,^{5,*} S. Kimura,⁵ M. Hagiwara,⁵ K. Kindo,⁶ A. Ya. Shapiro,⁷ and L. N. Demianets⁷

¹*P. L. Kapitza Institute for Physical Problems RAS, 119334 Moscow, Russia*

²*Neutron Scattering Science Division, Oak Ridge National Laboratory, Oak Ridge, Tennessee 37831-6393, USA*

³*CEA-Grenoble, DRFMC-SPSMS-MDN, 17 rue des Martyrs, 38054 Grenoble Cedex 9, France.*

⁴*Department of Physics, University of Warwick, Coventry, CV4 7AL, UK*

⁵*Center for Quantum Science and Technology under Extreme Conditions (KYOKUGEN), Osaka University, 1-3 Machikaneyama, Toyonaka, Osaka 560-8531, Japan*

⁶*Institute for Solid State Physics (ISSP), University of Tokyo, 5-1-5 Kashiwanoha, Kashiwa, Chiba 277-8581, Japan*

⁷*A. V. Shubnikov Institute for Crystallography RAS, 117333 Moscow, Russia*

(Dated: July 17, 2008)

The entire magnetic phase diagram of the quasi two dimensional (2D) magnet on a distorted triangular lattice $\text{KFe}(\text{MoO}_4)_2$ is outlined by means of magnetization, specific heat, and neutron diffraction measurements. It is found that the spin network breaks down into two almost independent magnetic subsystems. One subsystem is a collinear antiferromagnet that shows a simple spin-flop behavior in applied fields. The other is a helimagnet that instead goes through a series of exotic commensurate-incommensurate phase transformations. In the various phases one observes either true 3D order or quasi-2D order. The experimental findings are compared to theoretical predictions found in literature.

Helical magnetic structures in frustrated spin networks have been known for several decades, see, e.g. [1, 2, 3, 4]. The interest in this phenomenon was recently rekindled by a discovery of a new class of multiferroic compounds, where ferroelectricity is inherently connected to chiral incommensurate magnetic order (e.g. [5, 6]). The latter enables a coupling between the ferroelectric order parameter and a magnetic field, usually forbidden due to their respective symmetries. Perhaps the simplest, yet fundamentally the most important model that can provide the necessary chiral state is the two-dimensional triangular-lattice antiferromagnet (TLAF) that has a well-known “120°” spin structure.

A spectacular example of a multiferroic behavior due to the TLAF environment was recently found in the layered molybdenate $\text{RbFe}(\text{MoO}_4)_2$ [7]. In that material triangular planes of almost classical Fe^{3+} $S = 5/2$ spins are well separated by non-magnetic MoO_4 layers. The Fe^{3+} subsystem is an almost perfect realization of the TLAF model [8, 9]. In $\text{RbFe}(\text{MoO}_4)_2$ an external magnetic field disrupts the chiral magnetic structure and thereby removes the multiferroic effect. Even more interesting behavior can be expected in materials with a slightly distorted TLAF spin network. The distortion will unbalance the 120° structure and produce an incommensurate planar spin spiral. In an external magnetic field, theory predicts a multitude of exotic incommensurate and commensurate, chiral and centrosymmetric phases [2]. The chiral states could, at least in principle, possess multiferroic properties. The focus of this work is $\text{KFe}(\text{MoO}_4)_2$, a material structurally similar to $\text{RbFe}(\text{MoO}_4)_2$ but one that actually realizes the *distorted* TLAF model. Using a combination of experimental techniques, we find a remarkably complex magnetic phase diagram with *co-*

existing collinear and helical structures, ordered in either three or two dimensions.

At high temperatures $\text{KFe}(\text{MoO}_4)_2$ has a perfect triangular spin network due to the crystal symmetry of D_{3d}^3 group with $a = 5.66$ Å and $c = 7.12$ Å. The distortion occurs as a result of a crystallographic phase transition at $T = 311$ K [10, 11]. The low-temperature phase is monoclinic, with a doubling of the period along the c axis. Each Fe-plane becomes a distorted triangular lattice with two unequal exchange constants J_1 and J_2 (Fig. 1). Moreover, the adjacent Fe-layers become crystallographically inequivalent, with exchange constants J'_1 and J'_2 . The actual lattice distortion is too small to be detected with the resolution of our experiments, and we shall henceforth adopt a hexagonal lattice notation. A previous ESR study [12] of $\text{KFe}(\text{MoO}_4)_2$ came to a seemingly paradoxical conclusion: at low temperatures, in zero field, a helical spin structure coexists with a collinear state. It was hypothesized that the two type of magnetic order reside almost independently in the two inequivalent types of distorted triangular spin lattices, referred to as “S-layers” and “C-layers”, respectively.

To verify this bold assumption we performed magnetic neutron diffraction experiments using single-crystal samples from the same batch [12]. The crystals are transparent thin plates, of a natural triangular shape, typically 1-5 mg, with the planes of natural growth perpendicular to the 3-fold axis. The data were taken on the HB-1 and HB-1A 3-axis spectrometers at ORNL operating in 2-axis mode, using a Pyrolytic Graphite PG(002) monochromator to select $\lambda = 2.46$ Å for HB-1 and $\lambda = 2.37$ Å for HB-1A. At low temperatures, two sets of magnetic Bragg peaks emerge, with propagation vectors $(1/3 - \zeta, 1/3 - \zeta, 0)$, $\zeta = 0.038$, and $(1/2, 0, 0)$, respec-

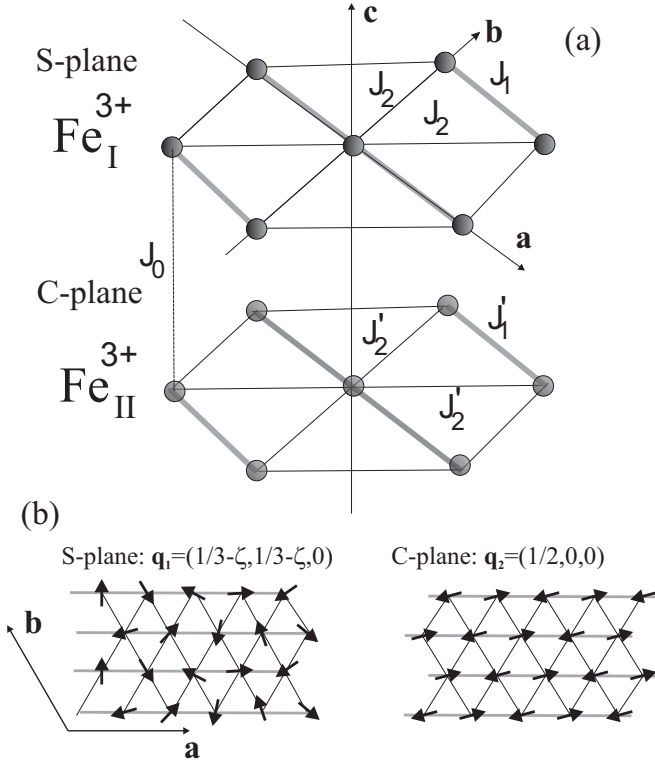


FIG. 1: (a) Arrangement of magnetic ions in the crystal structure of $\text{KFe}(\text{MoO}_4)_2$ showing two inequivalent Fe^{3+} planes. (b) Schematic representation of the zero-field magnetic structure.

tively. The observed ordering temperatures for the two sets of reflections are identical within experimental accuracy: $T_N = 2.4$ K. An analysis of 19 inequivalent Bragg reflections in the $(h, k, 0)$ plane at $T = 1.5$ K revealed that the $(1/3 - \zeta, 1/3 - \zeta, 0)$ peaks can be entirely accounted for by a planar helimagnetic state, with spins rotating in the (a, b) plane. At the same time, the 14 inequivalent sets of $(1/2, 0, 0)$ -type Bragg intensities measured in the $(h, k, 0)$ plane are consistent with a collinear AF spin arrangement, with spins in the (a, b) plane and forming a small angle of 15° with the a axis. Thus the diffraction data confirm the original two-layer model depicted in Fig. 1b. As discussed in Ref. [12], the drastically different spin arrangement in C- and S-layers can be accounted by the difference in the corresponding ratios $R = J_1/J_2$ vs. $R' = J'_1/J'_2$: theory predicts a switch from a helimagnetic to a collinear state at $R > 2$ [2].

The complexity of the $H - T$ phase diagram of $\text{KFe}(\text{MoO}_4)_2$ was revealed in bulk magnetic and calorimetric measurements. Steady-state magnetization data were collected in fields up to 12 T using an Oxford Instruments vibrating sample magnetometer and specific heat data were collected on a Quantum Design PPMS at Warwick University. High-field magnetization data were taken in the fields up to 25 T using a pulsed magnet at the KYOKUGEN center. Typical experimental $C(T)$

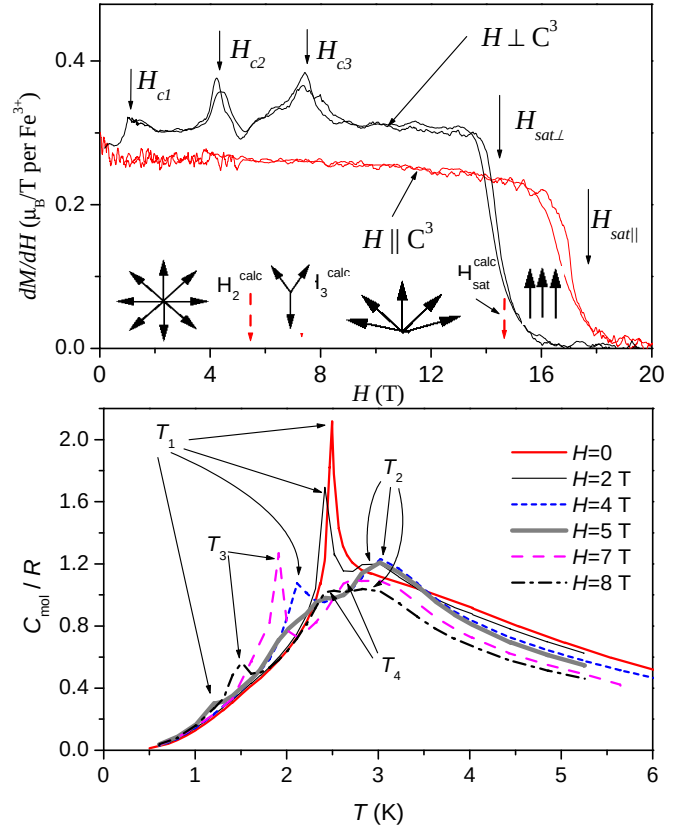


FIG. 2: (Color online)(a) Field derivative of the magnetization measured at $T = 1.6$ K. Solid arrows are experimentally observed anomalies. Dashed arrows and spin diagrams are explained in the text. (b) Specific heat measured on a 1mg $\text{KFe}(\text{MoO}_4)_2$ single crystal sample in magnetic fields applied in the (a, b) plane.

and dM/dH curves are shown in Fig. 2. In zero field we observe a sharp specific heat anomaly at $T_1 = 2.5$ K. In a magnetic field applied in the (a, b) plane this anomaly shifts to lower temperatures and survives up to $H = 5$ T. For $H > 2$ T an additional peak is observed at $T_2 > T_1$. Beyond $H > 5$ T the T_1 anomaly is replaced by a new feature at T_3 . The latter also moves to lower temperatures with increasing field. Yet another maximum in specific heat is observed at $T_4 < T_2$ in the high field regime. In the magnetization data, for a field applied along the c axis, the only observed feature is saturation at $H_{\text{sat}\parallel} = 16.9$ T. However, for a field in the (a, b) plane, the magnetization curves show four distinct anomalies. A jump of the field derivative of magnetization dM/dH at $H_1 \sim 1.2$ T is followed by sharp maxima at $H_2 \simeq 4.5$ T and $H_3 \simeq 7.5$ T. Finally, a saturation is reached at $H_{\text{sat}\perp} = 14.5$ T. For different orientations of the field within the (a, b) plane, and for samples with varying populations of the three crystallographic domain types, the measured magnetization curves are very similar. In particular, the angular variation of H_2 and H_3 is 10% and 7%, respectively. Some samples show a smeared peak in

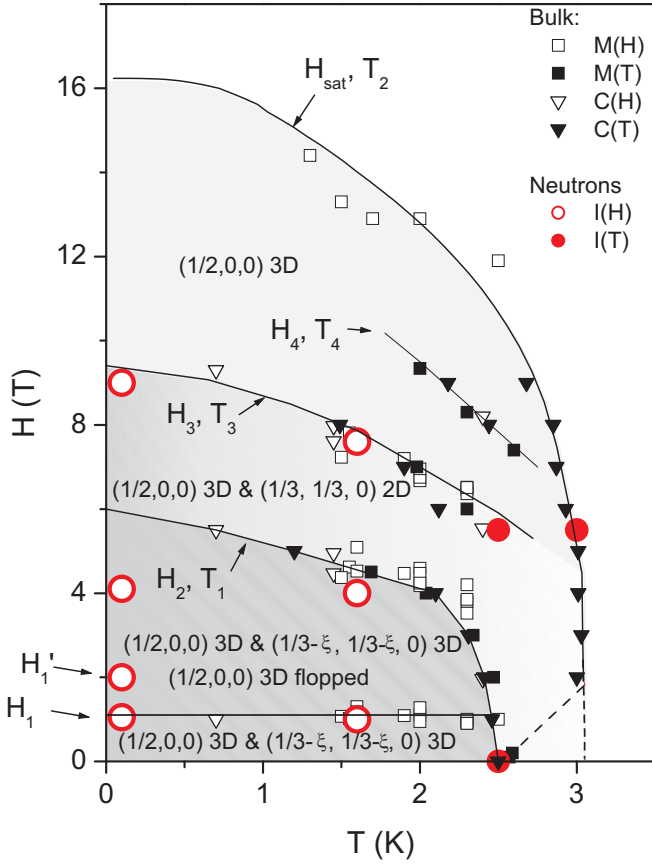


FIG. 3: (Color online) Cumulative magnetic phase diagram of $\text{KFe}(\text{MoO}_4)_2$ for a magnetic field applied in the (a,b) plane.

dM/dH in the field range above 8 T in the temperature interval $2\text{ K} < T < 2.5\text{ K}$. This anomaly, presented by the magnetic field H_4 in Fig. 3, was not visible in the sample used for pulse measurements. The magnetic and thermodynamic anomalies described above, together with the $M(T)$ data from Ref. [12], allow us to reconstruct the entire $H - T$ phase diagram, as shown in Fig. 3. The low-field part of the phase boundary at T_2 is uncertain because of the absence of this anomaly at $H < 2\text{ T}$.

The propagation vectors in the various phases were determined in neutron experiments on the D23 lifting counter diffractometer at ILL using a PG(002) monochromator and $\lambda = 2.38\text{ \AA}$ neutrons. The field was applied along the b axis (in hexagonal notations). Sample environment was a dilution refrigerator. Typical measured field dependencies of Bragg intensities are shown in Fig. 4. At $T = 100\text{ mK}$ the intensities of commensurate $(1/2, 0, 0)$ -type peaks go through two consecutive jumps at $H_1 = 1.3\text{ T}$ and $H'_1 = 2.1\text{ T}$. These transitions seem to have no effect on the incommensurate reflections. At $T = 1.5\text{ K}$ a single intensity jump is detected at $H_1 = 1\text{ T}$. As previously discussed in [12], the transition is to be associated with a spin flop in the C -planes, all moments rotating to be perpendicular to the

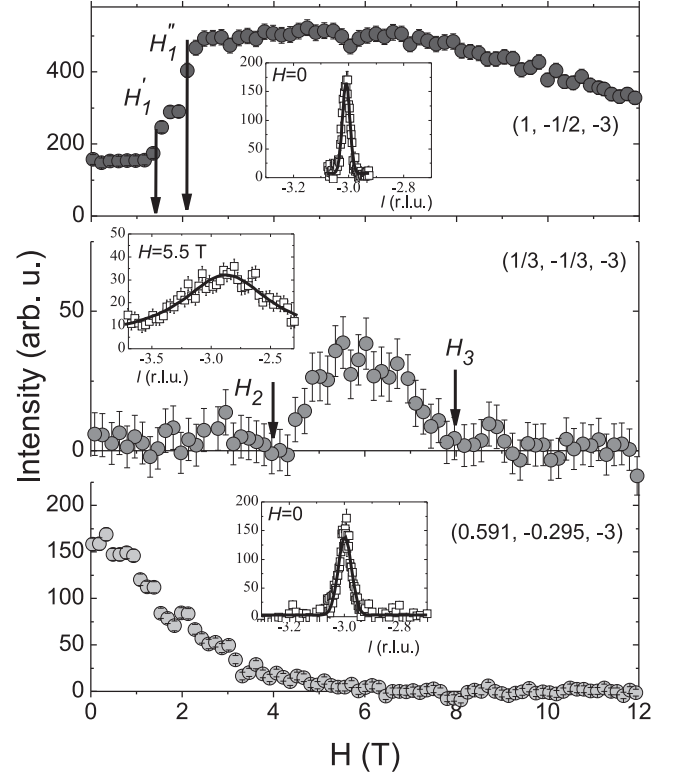


FIG. 4: Main panels: field dependencies of magnetic Bragg intensities measured in $\text{KFe}(\text{MoO}_4)_2$ at $T = 100\text{ mK}$. Insets: typical l -scans measured across the corresponding reflections.

applied field. The additional transition seen at low temperature at H'_1 requires further investigation. At higher fields all the action occurs within the S -planes. The intensity of the incommensurate $(1/3 - \zeta, 1/3 - \zeta, 0)$ -type reflections decreases and vanishes beyond $H_2 \sim 4\text{ T}$. Within experimental resolution the value of the magnetic propagation vector is field-independent. Beyond H_2 the $(1/3 - \zeta, 1/3 - \zeta, 0)$ -type peaks are replaced by *commensurate* reflections of type $(1/3, 1/3, 0)$. The latter first increases in intensity, peaks at around 6 T, and decreases at higher fields to vanish at $H_3 \sim 8 - 9\text{ T}$. At still higher fields, no magnetic reflections were found on either the $(h, h, 0)$, $(1/3 - \zeta, 1/3 - \zeta, l)$, or $(1/3, 1/3, l)$ reciprocal-space rods. At the temperature of neutron measurements ($T = 100\text{ mK}$ and $T = 1.5\text{ K}$) we found no signature of a high-field transition that could be associated with the T_4 -anomaly described above.

A remarkable feature of the neutron data is the different dimensionality of magnetic ordering in the different phases. Scans across the $(1/2, 0, 0)$ -type and $(1/3 - \zeta, 1/3 - \zeta, 0)$ -type reflections are resolution-limited along the h -, k - and l - directions. In contrast, the $(1/3, 1/3, 0)$ -type peaks in the regime $H_2 < H < H_3$ are actually Bragg rods parallel to the c axis, stretching across much of the Brillouin zone in the l -directions. The

corresponding c -axis correlation length is only 6 lattice units. The measured correlation length within the (a, b) plane is much larger, about 100 lattice units. The 2D character of the ordering persists in samples cooled in a 6 T applied field. The transition to the short range ordered state at T_2 naturally demonstrates a smeared $C(T)$ anomaly in contrast to a sharp peak at the transition to the 3D ordered phase at T_1 .

Guidance to understanding the complex phases realized in the S -planes can be drawn from the theoretical work of Ref. [2]. At first, we can estimate the relevant exchange parameters from the saturation fields and susceptibility. Because the neutron reflections observed in high fields correspond to C -planes, we assume the saturation is associated with this kind of planes, though S -planes, naturally, also give a contribution to the magnetization. For the C -planes, the saturation fields are given by: $g\mu_B H_{\text{sat}\perp} = 8(J'_1 + J'_2)S$ and $g\mu_B H_{\text{sat}\parallel} = 8(J'_1 + J'_2)S + 2DS$, respectively, where D is the single-ion easy-plane anisotropy defined as in [9]. Using the observed values of $H_{\text{sat}\perp}$ and $H_{\text{sat}\parallel}$ we get $J'_1 + J'_2 = 0.96$ K and $D' = 0.32$ K. Beyond the spin-flop at H_1 , the C -planes contribution to magnetic susceptibility should be constant: $\chi_C = g^2\mu_B^2/[8(J'_1 + J'_2)]$. Subtracting this value from dM/dH data for $H_{c1} < H < H_{c2}$ we obtain the susceptibility of the S -planes: $\chi_S \simeq 0.12 \mu_B/\text{T}$ per Fe^{3+} ion. Using the latter value and the measured $\zeta = 0.038$, by applying the equations in Ref. [2], we get $J_1 = 0.37$ K; $J_2 = 0.69$ K. As a self-consistency check, the experimental ratio $R = 0.53$ warrants a helimagnetic ground state for the S -layers in zero field [2].

Now, the measured values ζ and $H_{\text{sat}\perp}$ can be applied to reconstruct the phase transitions in the S -planes. The critical fields $H_2^{\text{calc}} = 5.7$ T, $H_3^{\text{calc}} = 7.2$ T, calculated by use of ζ and H_{sat} following the theory [2], are shown in dashed lines in Fig. 2a. As indicated by the arrow diagrams, and in perfect agreement with the diffraction experiments, at low fields one expects an incommensurate spiral structure confined to the (a, b) plane. Beyond the phase transition at H_2^{calc} the spins should form a commensurate 3-sublattice configuration with the 2D propagation vector $(1/3, 1/3)$, as observed experimentally. At still higher fields, beyond H_3^{calc} , the incommensurate state is expected to be restored. The spins will form a modulated fan-type structure, this time oscillating near the field direction in a small angular interval, still remaining within the (a, b) plane. Note that neutron diffraction failed to detect any incommensurate peaks beyond H_3^{calc} . This implies that either the system remains disordered, or that the ordering vector is outside our search range in reciprocal space and was simply overlooked. Besides, the flop of the spin plane perpendicular to the field direction is expected [2] at $H = H_{sf} = 6.5$ T. Instead of this instability we observe a loss of the magnetic Bragg peaks from S -planes.

It is remarkable that even as the S -plane go through a series of phase transitions, the C -planes remain unaffected, and vice versa. This implies that magnetic interactions between each type are direct, rather than mediated by the intercalated layers of the other type. These long-range interactions are likely to be of dipolar origin.

In summary, we have demonstrated that $\text{KFe}(\text{MoO}_4)_2$ realizes not just one, but *two* co-existing and decoupled instances of the distorted TLAF model. While one has a commensurate ground state and rather simple behavior in applied fields, the other features a chiral incommensurate structure and a series of exotic high-field phases. Future work should consider the possibility of multiferroic behavior associated with the S -layers.

Research at ORNL was funded by the US Department of Energy, Office of Basic Energy Sciences - Materials Science, Contract No. DE-AC05-00OR22725 with UT-Battelle, LLC. The work at Kapitza Institute is supported by the Russian Foundation for Basic Research. The work at Warwick University is supported by EP-SRC grant. A portion of this work was done as a part of a Foreign Visiting Professor Program in KYOKUGEN, Osaka University.

* Present address: Hitachi, Ltd., Hitachi Systemplaza, ShinKawasaki, 890 Kashimada, Saiwai, Kawasaki, Kanagawa, 212-8567, Japan

- [1] A. Yoshimori, J. Phys. Soc. Jpn. **14**, 807 (1959).
- [2] T. Nagamiya, K. Nagata and Y. Kitano, Progr. Theor. Phys. **27**, 1253 (1962).
- [3] M. E. Zhitomirsky, Phys. Rev. B **54**, 353 (1996).
- [4] Y. Tokiwa, T. Radu, R. Coldea, H. Wilhelm, Z. Tylchinski, F. Steglich, Phys. Rev. B **73**, 134414 (2006).
- [5] T. Kimura, T. Goto, H. Shintani, K. Ishizaka, T. Arima, Y. Tokura, Nature **426**, 55 (2003).
- [6] M. Kenzelmann, A. B. Harris, S. Jonas, C. Broholm, J. Schefer, S. B. Kim, C. I. Zhang, S.-W. Scheong, O. P. Vajk and J. W. Lynn, Phys. Rev. Lett. **95**, 087206 (2005).
- [7] M. Kenzelmann, G. Lawes, A. B. Harris, G. Gasparovic, C. Broholm, A. P. Ramirez, G. A. Jorge, M. Jaime, S. Park, Q. Huang, A. Ya. Shapiro, and L. A. Demianets, Phys. Rev. Lett. **98**, 267205 (2007).
- [8] A. I. Smirnov, H. Yashiro, S. Kimura, M. Hagiwara, Y. Narumi, K. Kindo, A. Kikkawa, K. Katsumata, A. Ya. Shapiro, and L. N. Demianets, Phys. Rev. B **75**, 134412 (2007).
- [9] L. E. Svistov, A. I. Smirnov, L. A. Prozorova, O. A. Petrenko, L. N. Demianets, and A. Ya. Shapiro, Phys. Rev. B **67**, 094434 (2003).
- [10] R. F. Klevtsova, P. V. Klevtsov, Kristallografia, **15**, 953 (1970).
- [11] G. A. Smolensky, I. G. Sinii, E. G. Kuzminov, E. F. Dudnik, Izv. AN SSSR ser. fiz. **43**, 1650 (1979).
- [12] L. E. Svistov, A. I. Smirnov, L. A. Prozorova, O. A. Petrenko, A. Ya. Shapiro and L. N. Dem'yanets, JETP Lett. **80**, 204 (2004).